

# Influence of Sliding Speed on the Tribological Characteristics of Pongamia Oil with TiO<sub>2</sub> Nanoparticles

Yashvir Singh<sup>1</sup>, Abhishek Sharma<sup>2\*</sup>, S.P. Dwivedi<sup>3</sup>, V.R.Mishra<sup>4</sup>, Ashish Kumar Srivastava<sup>5</sup>

<sup>1</sup>Department of Mechanical Engineering, Sir Padampat Singhania University, Udaipur, Rajasthan, INDIA,

<sup>2,3,4,5</sup>G. L. Bajaj Institute of Technology & Management, INDIA

\*Corresponding author E-mail: [absk2001@gmail.com](mailto:absk2001@gmail.com)

## Abstract

Environment degradation and non-biodegradability are the major problems associated with mineral-oil based lubricants. Non-edible vegetable oils are one of the suitable substitutes for the mineral oils. In this study, pongamia oil was used as the lubricant to check its feasibility for the tribological behaviour. TiO<sub>2</sub> nanoparticles are added to the pongamia oil on a weight-percentage basis. The variation of TiO<sub>2</sub> nanoparticles concentration with pongamia oil was evaluated for the coefficient of friction and wear analysis. Minimum coefficient of friction and wear was observed at 0.1 % concentration which gets further increased at 0.2 % concentration. The smooth surface of the pin was observed at 0.1 % nanoparticles concentration with the comparison to base pongamia oil.

**Keywords:** Pin-on-disk; pongamia oil; TiO<sub>2</sub> nanoparticles; Coefficient of friction; Specific wear rate.

## 1. Introduction

Mineral oils are suitable for various applications including fields related to manufacturing, automobile industries [1,2]. They are capable to act as a lubricant required for the reduction of friction and wear of the metals in contact during sliding motion. Mineral oils are the petroleum products and added with some additives to improve their performance according to the applications [3]. But, they are having adverse effects on the environment especially, regarding their disposal. The aquatic environment gets polluted due to their disposal and the petroleum reserves are going to deplete in the upcoming future [4]. There is a need to find alternative which can be utilized for the replacement of mineral oil. Taking this point into consideration, the author focused on finding alternatives to mineral oil.

Non-edible vegetable oils are one of the resources and play a vital role in enhancing the renewable resources, more economic and harmless to the environment where it is used [5,6]. Non-edible vegetable oils are having better biodegradability in comparison to petroleum-based mineral oils but they lag in technical properties with respect to the conventional lubricants [7]. Oxidation stability is less and the main problems have occurred at low temperature with a reduction in pour point and cloud point values [8]. Non-edible vegetable oils are having certain advantages like better equipment life, minimum emission hooked on the atmosphere, better lubricity, improved anti-wear characteristics and excessive viscosity index [9].

For the further improvement of the physicochemical properties, nanoparticles are one of the suitable additives [10,11,12]. Numerous studies have been steered related to the effect of nanoparticles for the tribological characteristics but most of them are regarding to their addition with synthetic or mineral oil. Chen *et al.* [13] coated Cu-Ni bimetallic nanoparticles surface with dodecanethiol and investigated its tribological characteristics. Better

dispersibility was observed with Cu-Ni bimetallic nanoparticles due to its hydrophobic nature. Cu-Ni nanoparticles performed well as an additive for reducing friction and wear of the surface during tribological investigation. Huang *et al.* [14] performed tribological characteristics of graphite nanosheets with an average diameter of 500 nm by stirring ball milling. Improvement in the antiwear characteristics of paraffin oil was improved by the addition of graphite nanosheets. TiO<sub>2</sub> nanoparticles have obtained considerable importance as they are suitable for reducing friction and wear of the material due to the mending mechanism or they are having the capacity of forming a sustainable protective film [15]. From the above reference survey, very few studies have looked at the effect of TiO<sub>2</sub> nanoparticles upon the friction plus wear individualities of lubricant which have significant influence on the friction and the anti-wear mechanism. Based on the aforementioned literature survey, the author has determined that the addition of TiO<sub>2</sub> nanoparticles with pongamia oil is suitable for the improvement of the lubrication characteristics of bare pongamia seed oil. Therefore, the purpose of this study is to investigate the tribological characteristics of nanoparticles as a pongamia oil additive and reveal its characteristics about its feasibility as an alternative to bare pongamia oil at different sliding speeds.

## 2. Experimental Details

### 2.1. Lubricant development

To obtain a uniform and stable disparity, nanoparticles were added to the macadamia oil using ultra sonication technique. The ultrasonic was used to perform mixing of TiO<sub>2</sub> nanoparticles with pongamia oil. The duration of the test was 1.5 h and the concentration of the nanoparticles ranging from 0.1% to 0.3% (gap of 0.1%) was added to the macadamia oil at ambient temperature. The addition of the nanoparticles to the pongamia oil was designated as PO, PO+0.1, PO+0.2, and PO+0.3 respectively.

### 2.2. Experimental Setup

The physicochemical properties of the PO, PO+0.1, PO+0.2, and PO+0.3 was mentioned in Table 1.

**Table 1:** Physicochemical properties of bare pongamia oil and nanoparticles concentrations with the pongamia oil.

S. No.	Properties	Viscosity (cSt) 40 °C	Viscosity (cSt) 100 °C	Flash point (°C)	Fire point (°C)
1.	Pongamia oil	243.14	18.12	272	259
2.	Pongamia oil+0.1%	245.12	18.23	272.1	262
3.	Pongamia oil +0.2%	246.29	18.34	272.5	269
4.	Pongamia oil +0.3%	246.48	19.45	272.6	273

A pin-on-disk machine was expended to perform the wear and friction test according to the ASTM standards D4172 and G99 [16]. The pin material used for present study was a combination of Al-7%Si alloy and EN31 steel. The hardness of the EN31 steel was 60 HRC. The details about the operating conditions during the experiment was illustrated in Table 2. The flow rate of about 5 ml/min was maintained during the experiment for the operating conditions. The flow rate was calculated by flowing the oil into the measuring flask and the time was determined according to the flow for filing the flask. The material loss of the pin was calculated by the difference of pin weight before and after performing the test experiment. Shimadzo weighing machine was used for the weighing purpose of the pin with having an accuracy of ±0.1 mg. The acetone was used to clean the pin surface with ultrasonic bath apparatus operated at 65°C temperature for around 15 minutes.

**Table 2:** Operating conditions during the test


S. No.	Operating parameters	Value
1.	Normal loads applied on the pin	40 N
2.	Track length used during the test	80 mm
3.	Sliding speed, rpm	100-400 (with a gap of 100)
4.	Total sliding distance	3000 m

### 3. Results and Discussion

Test with the bare pongamia oil was used as the reference for the COF characteristics and wear behavior.


#### 3.1. Coefficient of Friction Analysis

A summary of the coefficient of friction for altered sliding speed at particular load of 40 N is gathered in Fig. 1. The sliding speed was assorted from 100 rpm to 400 rpm with a gap of 100 RPM. Through an increase in sliding speed, the coefficient of friction decreases having a minimum coefficient of friction at 400 rpm. With an increase in speed, the duration of the contacts between the sliding parts decreases resulting in a reduction of coefficient of friction.

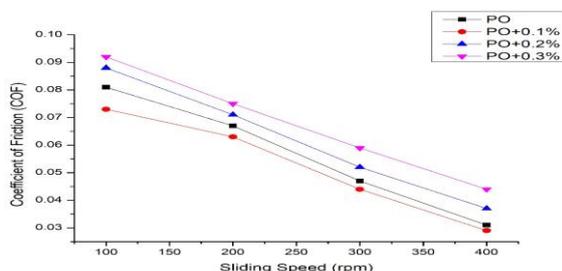

**Figure 1:** Coefficient of friction with sliding speed

Fig. 2 displays the effect of the concentration of copper nanoparticles on the coefficient of friction at various sliding speeds with 40 N load. With an increase in the amount of concentration of nanoparticles, minimum coefficient of friction was obtained up to the limit of 0.1% concentration and a further increase in the value of the coefficient of friction was obtained after 0.2 % concentration at each sliding speed ranging from 100 rpm to 400 rpm.

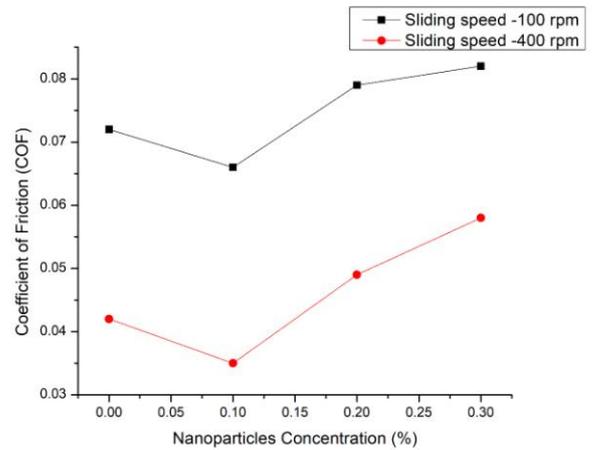


**Figure 2:** Effect of nanoparticles concentration on COF.

This may be attributed to the deposition of nanoparticles to the pin surface resulting in a strong protective film between oil, nanoparticles and surfaces [16,17]. With increase in concentration of nanoparticles behind the optimum concentration limit i.e. 0.1 %, deep interaction of the cu nanoparticles with the surface promoted to the increase in coefficient of friction.

#### 3.2. Wear Analysis

Effect of sliding speed on the specific wear rate of bare pongamia oil and concentration of TiO<sub>2</sub> nanoparticles is shown in Fig. 3. With an increase in sliding speed, a decrease in the amount of wear was observed and maximum wear was obtained at 100 rpm. The reason of obtaining the maximum wear at low speed was contributed to the time available for the nanoparticles to interact with the surface. After 0.1 % concentration, more nanoparticles get accumulated and results in the wear of the surface. This was due to the concentration increase in the amount of nanoparticles.

Fig. 4 shows the effect of concentration of nanoparticles on specific wear rate at 40 N load. With an increase in concentration of nanoparticles, specific wear rate was reduced up to the limit of 0.1 % concentration and a further increase in the amount of wear rate was observed at 0.2 % concentration.

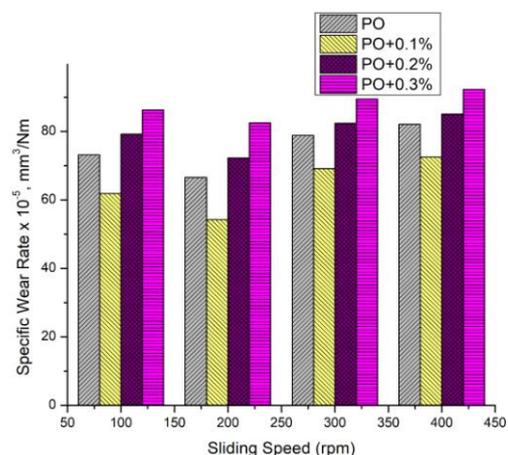

**Figure 3:** Effect of sliding speed on specific wear rate

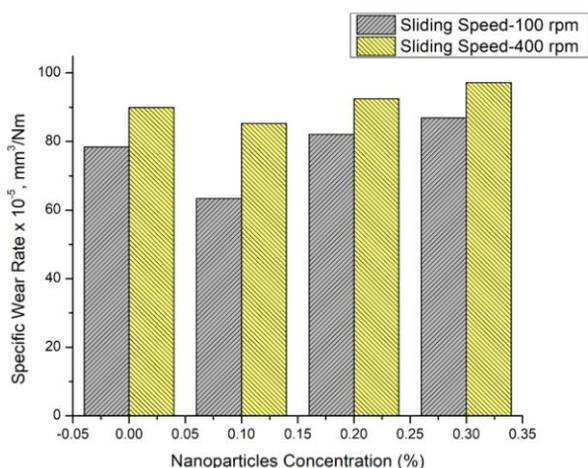


Figure 4: Nanoparticles concentration on specific wear rate.

## 4. Conclusions

The effect of  $\text{TiO}_2$  nanoparticles concentration was investigated to check the tribological behavior of surface equipped with macadamia oil. Friction reduction properties of the pongamia oil were improved by using  $\text{TiO}_2$  nanoparticles up to a certain level. Minimum wear was obtained at the optimum copper concentration of 0.1 %.

## References

- [1] Ahmer, S. M. H., L. S. Jan, M. A. Siddig and S. F. Abdullah (2016). "Experimental results of the tribology of aluminum measured with a pin-on-disk tribometer: Testing configuration and additive effects." *Friction* **4**(2): 124-134.
- [2] Ansari, N. A., A. Sharma and Y. Singh (2018). "Performance and emission analysis of a diesel engine implementing polanga biodiesel and optimization using Taguchi method." *Process Safety and Environmental Protection* **120**: 146-154.
- [3] Aravind, A., M. L. Joy and K. P. Nair (2015). "Lubricant properties of biodegradable rubber tree seed (Hevea brasiliensis Muell. Arg) oil." *Industrial Crops and Products* **74**: 14-19.
- [4] Chen, L., H. Xu, H. Cui, H. Zhou, H. Wan and J. Chen (2017). "Preparation of Cu-Ni bimetallic nanoparticles surface-capped with dodecanethiol and their tribological properties as lubricant additive." *Particuology* **34**: 89-96
- [5] Choi, Y., C. Lee, Y. Hwang, M. Park, J. Lee, C. Choi and M. Jung (2009). "Tribological behavior of copper nanoparticles as additives in oil." *Current Applied Physics* **9**(2, Supplement): e124-e127.
- [6] De Mello, J. D. B., C. Binder, G. Hammes, R. Binder and A. N. Klein (2017). "Tribological behaviour of sintered iron based self-lubricating composites." *Friction* **5**(3): 285-307
- [7] do Valle, C. P., J. Silva Rodrigues, L. M. U. D. Fechine, A. P. Cunha, J. Queiroz Malveira, F. M. T. Luna and N. M. P. S. Ricardo "Chemical modification of Tilapia oil for biolubricant applications." *Journal of Cleaner Production*.
- [8] Esipovich, A. L., A. E. Rogozhin, A. S. Belousov, E. A. Kanakov, K. V. Otopkova and S. M. Danov (2018). "Liquid-liquid equilibrium in the systems FAMES + vegetable oil + methyl alcohol and FAMES + glycerol + methyl alcohol." *Fuel* **217**: 31-37.
- [9] Hajar, M. and F. Vahabzadeh (2016). "Biolubricant production from castor oil in a magnetically stabilized fluidized bed reactor using lipase immobilized on  $\text{Fe}_3\text{O}_4$  nanoparticles." *Industrial Crops and Products* **94**: 544-556.
- [10] Huang, H. D., J. P. Tu, L. P. Gan and C. Z. Li (2006). "An investigation on tribological properties of graphite nanosheets as oil additive." *Wear* **261**(2): 140-144.
- [11] Liu, G., X. Li, B. Qin, D. Xing, Y. Guo and R. Fan (2004). "Investigation of the Mending Effect and Mechanism of Copper Nanoparticles on a Tribologically Stressed Surface." *Tribology Letters* **17**(4): 961-966.
- [12] Meng, H. N., Z. Z. Zhang, F. X. Zhao, T. Qiu, X. Zhu and X. J. Lu (2015). "Tribological behaviours of Cu nanoparticles recovered from electroplating effluent as lubricant additive." *Tribology - Materials, Surfaces & Interfaces* **9**(1): 46-53.
- [13] Panchal, T. M., A. Patel, D. D. Chauhan, M. Thomas and J. V. Patel (2017). "A methodological review on bio-lubricants from vegetable oil based resources." *Renewable and Sustainable Energy Reviews* **70**: 65-70.
- [14] Singh, Y., A. Farooq, A. Raza, M. A. Mahmood and S. Jain (2017). "Sustainability of a non-edible vegetable oil based bio-lubricant for automotive applications: A review." *Process Safety and Environmental Protection* **111**: 701-713.
- [15] Sonthalia, A. and N. Kumar (2017). "Hydroprocessed vegetable oil as a fuel for transportation sector: A review." *Journal of the Energy Institute*.
- [16] Syahrullail, S., S. Kamitani and A. Shakirin (2013). "Performance of Vegetable Oil as Lubricant in Extreme Pressure Condition." *Procedia Engineering* **68**: 172-177.
- [17] Wu, X., B. Yue, Y. Su, Q. Wang, Q. Huang, Q. Wang and H. Cai (2017). "Pollution characteristics of polycyclic aromatic hydrocarbons in common used mineral oils and their transformation during oil regeneration." *Journal of Environmental Sciences* **56**: 247-253.